AD-A093 074 NAVAL SURFACE WEAPONS CENTER SILVER SPRING MD F/G 20/3
MAGNETOSTRICTION OF LAVES PHASE RARE EARTH-NI2 COMPOUNDS,(U)
JUL 80 R ABBUNDI, A E CLARK
UNCLASSIFIED NSWC/TR-80-303 NL



END
DATE FILMED
[ 81
DTIC

NSWC TR 80-303



# MAGNETOSTRICTION OF LAVES PHASE RARE EARTH-$Ni_2$ COMPOUNDS

BY R. ABBUNDI, A. E. CLARK

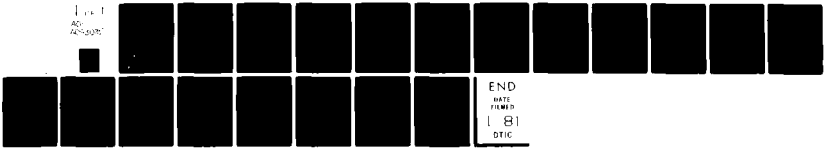RESEARCH AND TECHNOLOGY DEPARTMENT

1 JULY 1980



NAVAL SURFACE WEAPONS CENTER

Dahlgren, Virginia 22448 • Silver Spring, Maryland 20910

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

## REPORT DOCUMENTATION PAGE

READ INSTRUCTIONS BEFORE COMPLETING FORM

1. REPORT NUMBER: (14) NSWC/TR-80-303
2. GOVT ACCESSION NO.: AD-A093 074
3. RECIPIENT'S CATALOG NUMBER:

4. TITLE (and Subtitle): (6) MAGNETOSTRICTION OF LAVES PHASE RARE EARTH-$Ni_2$ COMPOUNDS
5. TYPE OF REPORT & PERIOD COVERED:
6. PERFORMING ORG. REPORT NUMBER:

7. AUTHOR(s): (10) R. Abbundi and A. E. Clark
8. CONTRACT OR GRANT NUMBER(s):

9. PERFORMING ORGANIZATION NAME AND ADDRESS:
Naval Surface Weapons Center
Research & Technology Department
Radiation Division, Solid State Branch R45
White Oak, Silver Spring, Maryland 20910

10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS:
61153N; RR 02-206; RR 02-206-01; R45AC

11. CONTROLLING OFFICE NAME AND ADDRESS:

12. REPORT DATE: (11) 1 July 1980
13. NUMBER OF PAGES: 20

14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office):

15. SECURITY CLASS. (of this report): UNCLASSIFIED
15a. DECLASSIFICATION/DOWNGRADING SCHEDULE:

16. DISTRIBUTION STATEMENT (of this Report)

Approved for public release; distribution unlimited.

17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)

18. SUPPLEMENTARY NOTES

To be published in IEEE *Transactions on Magnetics*

19. KEY WORDS (Continue on reverse side if necessary and identify by block number)

Magnetostriction
Rare Earth-Intermetallic Compounds
Rare Earth-Ni Compounds

20. ABSTRACT (Continue on reverse side if necessary and identify by block number)

The magnetostriction of the $RNi_2$ compounds (R = Tb,Dy,Ho,Er and Tm) was measured as a function of applied field from T = 5 K to above the Curie temperatures. A direct comparison is made between these results and the huge magnetostriction observed at cryogenic temperatures in the $RFe_2$ and $RCo_2$ compounds. The largest magnetostriction in the $RNi_2$ series occurs in $TbNi_2$. At T = 5 K the magnetostriction is fairly well saturated and results in a value of $\lambda_{\parallel} - \lambda_{\perp} = 270 \times 10^{-6}$ at H = 25 kOe, while extrapolation to infinite field yields $340 \times 10^{-6}$. $DyNi_2$ also displays a tendency to saturate at the higher fields

DD FORM 1 JAN 73 1473 EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-LF-014-6601

UNCLASSIFIED
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

100234 100227

411 553

at lower temperatures with $\lambda_{11} - \lambda_{\perp} = -765 \times 10^{-6}$ at 25 kOe and -840 ppm at H = ∞. The compounds HoNi$_2$, ErNi$_2$ and TmNi$_2$ all exhibit large strains at T = 5 K although fail to saturate with available fields. At 25 kOe the magnetostriction for these compounds was found to be ~~-586 x 10$^{-6}$~~, -415 x 10$^{-6}$ and ~~-552~~ x 10$^{-6}$ respectively.

# FOREWORD

The magnetostriction study reported here is part of a research program undertaken to determine the nature of the magnetostriction in the rare earth-intermetallic compounds. In this paper is detailed the temperature dependence of the magnetostriction for a series of rare earth-$Ni_2$ compounds. Studies were made as a function of applied field from T = 5 K to temperatures above the Curie points.

The largest magnetostriction in the $RNi_2$ series occurs in $TbNi_2$. At T = 5 K the magnetostriction is fairly well saturated and results in a value of $\lambda_{\parallel} - \lambda_{\perp} = 2270 \times 10^{-6}$ at H = 25 kOe, while extrapolation to infinite field yields $2340 \times 10^{-6}$. $DyNi_2$ also displays a tendency to saturate at the higher fields at lower temperature with $\lambda_{\parallel} - \lambda_{\perp} = -765 \times 10^{-6}$ at 25 kOe and -840 ppm at $H = \infty$. The compounds $HoNi_2$, $ErNi_2$, and $TmNi_2$ all exhibit large strains at T = 5 K although fail to saturate with available fields. At 25 kOe the magnetostriction for these compounds was found to be $-386 \times 10^{-6}$, $-415 \times 10^{-6}$ and $-552 \times 10^{-6}$ respectively.

The study was carried out in the Solid State Branch of the Radiation Division as part of the research program on magnetostrictive material. The research was sponsored by the Office of Naval Research (PO-4-0081, NR 039-110) and the NSWC Independent Research Program (IR-011).

B. F. DESAVAGE
By direction



CONTENTS



ILLUSTRATIONS

# INTRODUCTION

Intermetallic compounds of the rare earths with the 3d transition metals of Fe, Co and Ni have been the subject of extensive investigations at many laboratories. Many interesting effects have been observed in ultrasonic and magnetostriction measurements in the cubic Laves phase $RTM_2$ compounds, where large changes in the elastic moduli as well as huge magnetostriction constants occur.[1-7] In this work we report on the magnetostriction of the $RNi_2$ compounds (R = Tb, Dy, Ho, Er and Tm).

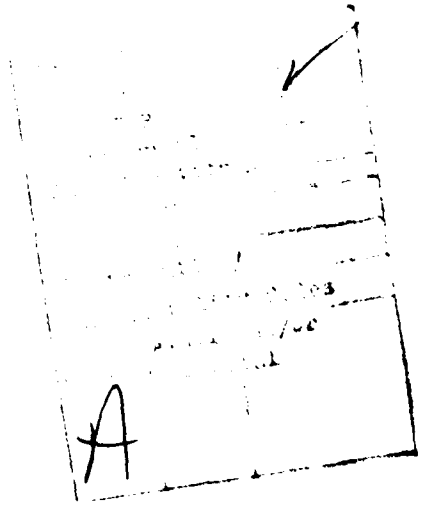Bulk magnetization measurements[8] on the $RNi_2$ series have shown that the Curie temperatures are in the cryogenic region with $T_c < 90$ K. Both $YNi_2$ and $LuNi_2$ were found to exhibit only a Pauli paramagnetic behavior down to 4.2 K. Thus it appears that Ni possesses no moment of its own in these compounds. This behavior is unlike that observed in the $RFe_2$ and $RCo_2$ compounds. In the case of the $RFe_2$ series the 3d transition element when combined with the heavy lanthanide elements Tb through Tm possesses a moment of approximately 1.6 $\mu_B$/Fe atom, with only a relatively small variation dependent upon the rare earth.[9,10] In the $RCo_2$ compounds the Co moment is approximately 1 $\mu_B$/Co atom.[11] The magnetization results[8] further showed that $GdNi_2$ at T = 0 possesses a saturation moment of 7.1 $\mu_B$, very nearly equal to the gJ value of the rare earth. However, the moments of the remaining $RNi_2$ compounds are substantially reduced from their theoretical gJ values. This discrepancy has been attributed to crystal field effects on the rare earth which partially quench the orbital angular momentum.[12]

Mössbauer effect measurements[13] on the $RNi_2$ compounds have shown that the easy axis of magnetization follows the same sequence as that observed for both the $RFe_2$[14] and $RCo_2$[15] series. $DyNi_2$ and $HoNi_2$ magnetize along a [100] direction, while $TbNi_2$ and $ErNi_2$ along a [111] direction. Although no results were reported on $TmNi_2$, it is assumed that $TmNi_2$ has its easy axis of magnetization along a [111] direction, similar to $TmFe_2$.[16]

The magnetostriction measurements were performed as a function of field from T = 5 K to above the Curie temperatures. These results can be directly compared with the huge magnetostriction which has been found at cryogenic temperatures in both the $RFe_2$[3-5] and $RCo_2$[6,7] series.

## EXPERIMENTAL RESULTS

The highly anisotropic 4f electron charge cloud of the $Tb^{3+}$ ion produces enormous magneto-strains in $TbFe_2$[3] and $TbCo_2$.[6,7] The high Curie temperature of $TbFe_2$ ($T_c$ = 710 K) allows this huge magnetostriction of $\lambda_{111}(0\ K) = 4400 \times 10^{-6}$ at T = 0 to remain large at room temperature, where $\lambda_{111}(300\ K) = 2500 \times 10^{-6}$. This strain is the largest room temperature magnetostriction of any known material. In $TbCo_2$ a similarly huge rhombohedral distortion develops below $T_c$ = 240 K, also reaching $4400 \times 10^{-6}$ at 4.2 K.

Gignoux et al.[7] state that $TbNi_2$, however, behaves quite differently. Rhombohedral distortions ($\lambda_{111}$), measured by x-ray diffraction, were found to be ≈ 0. They state that this small value is consistent with a smaller molecular field than found in either $TbFe_2$ or $TbCo_2$ resulting in a smaller value of $\langle O_2^0 \rangle$. Our results on the magnetostriction of $TbNi_2$ do not confirm this low measured value. Instead, we find that the strain in $TbNi_2$ is about 50% of that in $TbFe_2$ and $TbCo_2$. Figure 1 shows the magnetostriction at T = 5 K as a function of applied field for $TbNi_2$ and $DyNi_2$. The temperature dependence of the magnetostriction at H = 25 kOe for $TbNi_2$ and $DyNi_2$ is shown in Figure 2. At T = 5 K the magnetostriction of $TbNi_2$ is fairly well saturated and results in a value of $\lambda_{\parallel} - \lambda_{\perp} = 2270 \times 10^{-6}$ at H = 25 kOe, while extrapolation to infinite field yields $2340 \times 10^{-6}$.

$DyNi_2$ also displays a tendency to saturate with $\lambda_{\parallel} - \lambda_{\perp} = -765 \times 10^{-6}$ at 25 kOe. The magnitude of this strain while comparable to that observed in $DyCo_2$[6] implies a substantially larger $|\lambda_{100}|$ than was found in $DyFe_2$, where $|\lambda_{100}|$ remained small through the entire temperature range.[3]

The field dependence of the magnetostriction at T = 5 K for $HoNi_2$, $ErNi_2$ and $TmNi_2$ is shown in Figure 3. A peak in the magnetostriction of $HoNi_2$ was observed near H = 5kOe. We attribute this behavior to the large magnetocrystalline anisotropy which characterizes the $RTM_2$ compounds.[7,9,17-20] In the case of $HoNi_2$, as the field is increased above 5kOe, the moments are tilted away from their highly magnetostrictive easy [100] axes, decreasing the net strain. This behavior is only

observed at the lower temperatures. For T > 11 K the rapid decrease in anisotropy with increasing temperature results in the usual behavior of increasing $|\lambda|$ with increasing field. The magnitude of the peak strain in $HoNi_2$ at T = 5 K of -533 ppm is comparable to $\lambda_{100}$ measured in $HoFe_2$ where $\lambda_{100}(0\ K) = -745$ ppm.[5] The temperature dependence of the magnetostriction at H = 25 kOe for $HoNi_2$ is shown in Figure 4.

The large anisotropy in these materials is again reflected in the failure of $ErNi_2$ to reach saturation at 5 K, as shown in Figure 3. However, the magnetostriction is still large with $\lambda_{\parallel} - \lambda_{\perp} = -415 \times 10^{-6}$ at H = 25 kOe. Figure 5 shows the temperature dependence of the strain at 25 kOe, from 5 K to above the Curie temperature.

A comparison of the field dependence of the magnetostriction at 5 K between $TmNi_2$ (see Figure 3) and the other compounds shows a substantially different behavior. The magnetostriction is far from saturation. Farrell and Wallace, in their bulk magnetization measurements,[8] report that $TmNi_2$ may not be ferromagnetic at T = 2 K. They could not determine whether $TmNi_2$ was displaying VanVleck paramagnetism or the onset of ferromagnetism. However, in view of those findings, it appears that, at least at 5 K, $TmNi_2$ is not ferromagnetic and thus that accounts for the absence of any spontaneous magnetostriction at this temperature. Nevertheless at H = 25 kOe the strain is becoming quite large with $\lambda_{\parallel} - \lambda_{\perp} = -552 \times 10^{-6}$. In theory the saturation magnetostriction of $TmNi_2$ should be of comparable magnitude to that found in $TbNi_2$. The temperature dependence of the magnetostriction for $TmNi_2$ at 25 kOe is shown in Figure 6.

## REFERENCES


1. H. Klimker and M. Rosen, J. Magnetism and Magnetic Materials 7, 361 (1978).
2. S. Rinaldi and J. Cullen, Phys. Rev. B 18, 3677 (1978).
3. A. E. Clark, R. Abbundi, H. T. Savage and O. D. McMasters, Physica 86-88B, 73 (1977).
4. R. Abbundi and A. E. Clark, J. Appl. Phys. 49, 1969 (1978).
5. R. Abbundi, A. E. Clark and N. C. Koon, J. Appl. Phys. 50, 1671 (1979).
6. E. W. Lee and F. Pourarian, Phys. Stat. Sol. 34A, 383 (1976).
7. D. Gignoux, F. Givord, R. Perrier de la Bathie and F. Sayetat, J. Phys. F 9, 763 (1979).
8. J. Farrell and W. E. Wallace, J. Inorg. Chem. 5, 105 (1966).
9. A. E. Clark, R. Abbundi and W. R. Gillmor, IEEE Trans. on Magnetics Mag-14, 542 (1978).
10. W. E. Wallace, Prog. Rare Earth Sci Tech. 3, 1 (1968).
11. R. M. Moon, W. C. Koehler and J. Farrell, J. Appl. Phys. 36, 978 (1965).
12. B. Bleaney, Proc. R. Soc. 276A, 28 (1963).
13. S. K. Arif, I. Sigalas and D. St. P. Bunbury, Phys. Stat. Sol. 41A, 585 (1977).
14. G. J. Bowden, D. St. P. Bunbury, A. P. Guimaraes and R. E. Snyder, J. Phys. C 1, 1376 (1968).
15. U. Atzmony and G. Dublon, Physica 86-88B, 167 (1977).
16. G. K. Wertheim, V. Jaccarino and J. H. Wernick, Phys. Rev. 135, A151 (1964).
17. A. E. Clark, J. R. Cullen and K. Sato, AIP Conf. Proc. 24, 670 (1975).
18. A. E. Clark, AIP Conf. Proc. 18, 1015 (1973).
19. D. Gignoux, F. Givord and R. Lemaire, Phys. Rev. B 12, 3878 (1975).
20. U. Atzmony, M. P. Dariel, E. R. Bauminger, D. Lebenbaum, I. Nowick and S. Ofer, Phys. Rev. B 7, 4220 (1973).

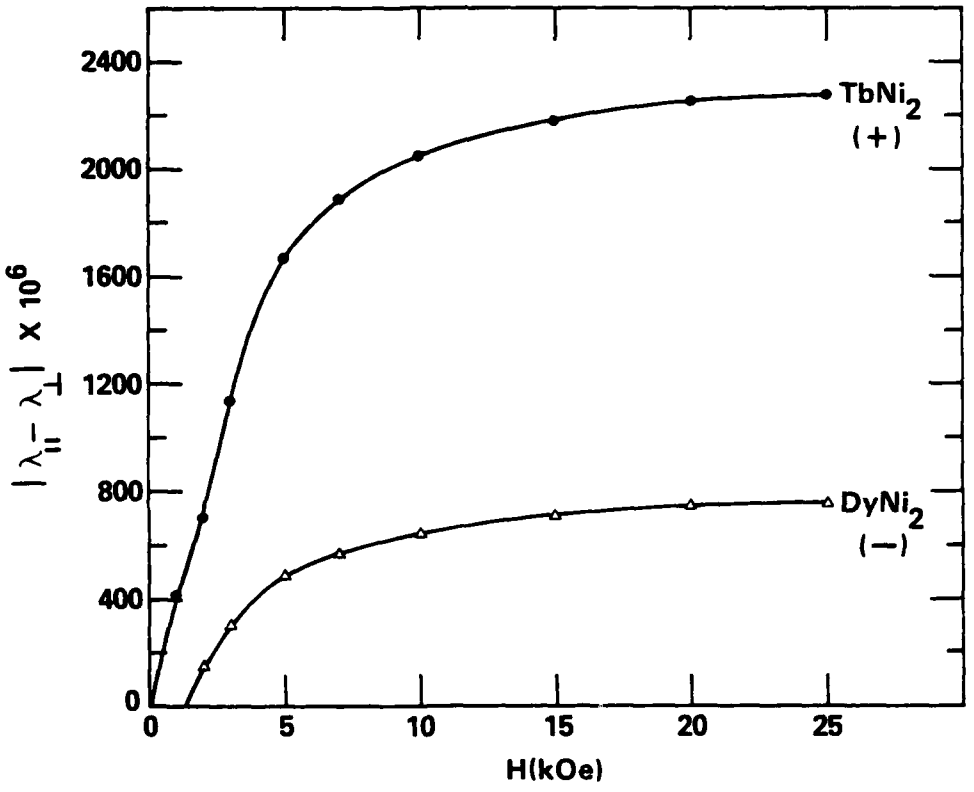


FIGURE 1 MAGNETOSTRICTION AT T=5K AS A FUNCTION OF APPLIED FIELD FOR $TbNi_2$ AND $DyNi_2$. THE MAGNETOSTRICTION OF $TbNi_2$ IS POSITIVE (+), WHILE $DyNi_2$ IS NEGATIVE (−).

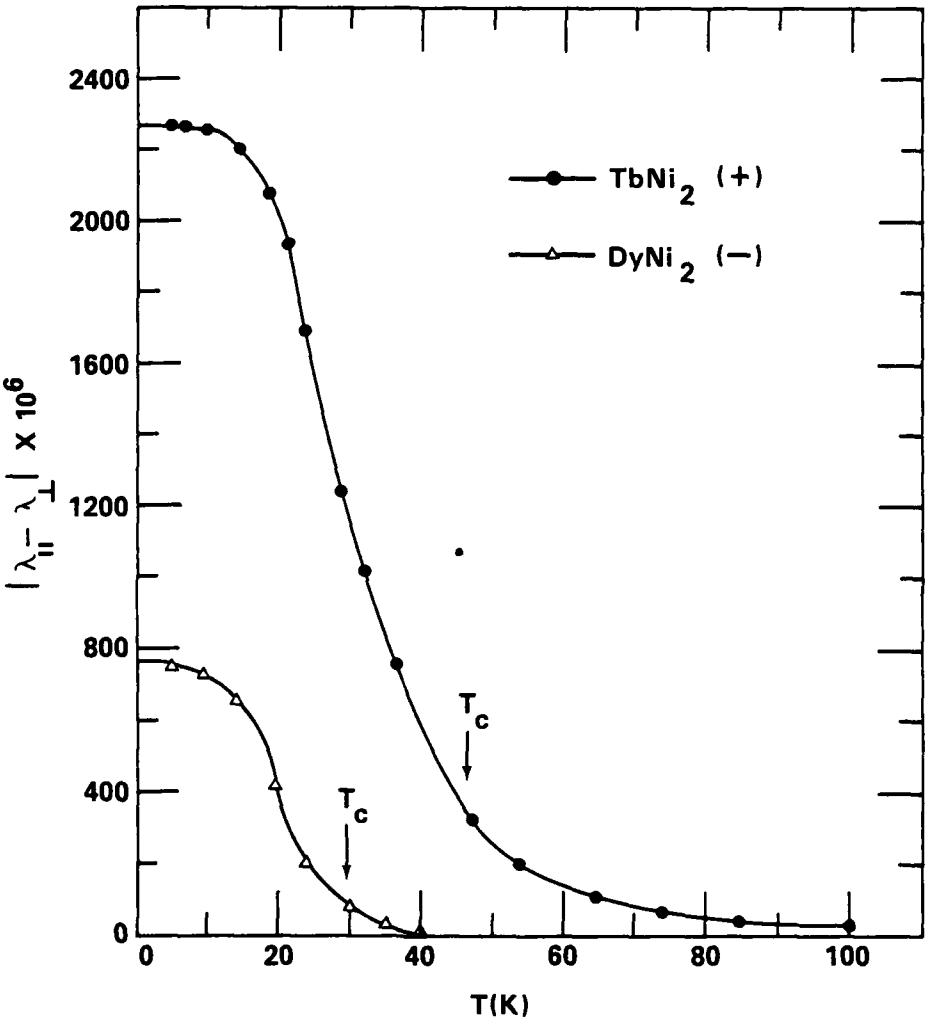


FIGURE 2 TEMPERATURE DEPENDENCE OF THE MAGNETOSTRICTION AT H=25kOe FOR $TbNi_2$ AND $DyNi_2$. THE CURIE TEMPERATURES WERE TAKEN FROM BULK MAGNETIZATION MEASUREMENTS (REF. 8).

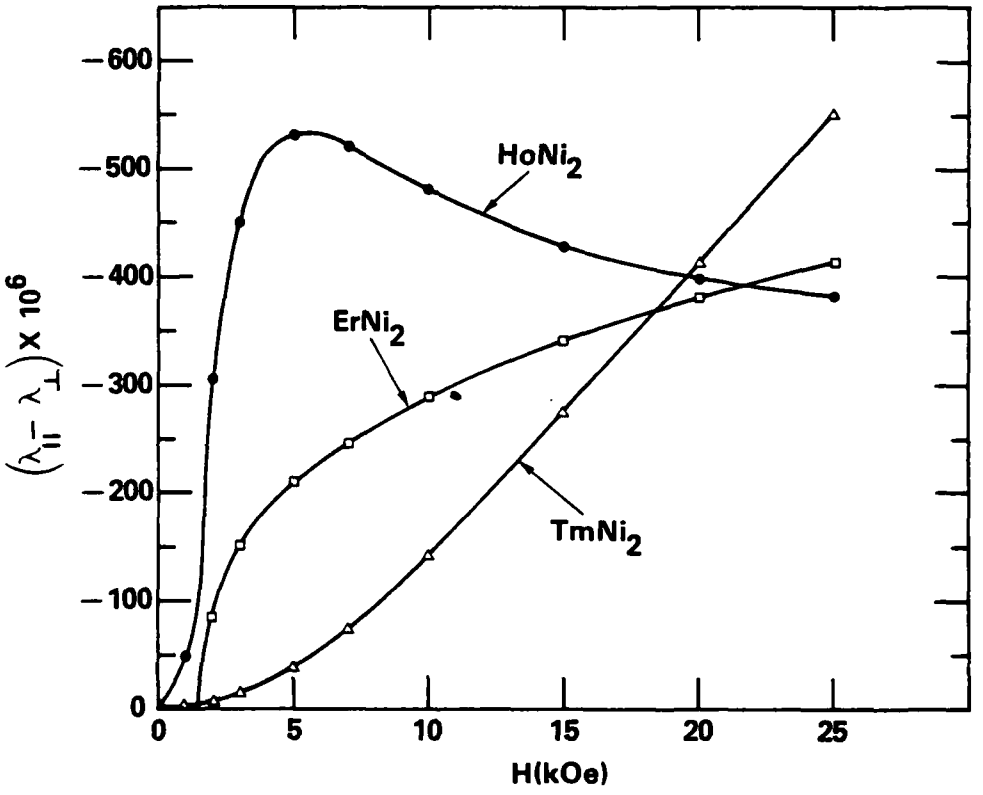


FIGURE 3 MAGNETOSTRICTION AT T=5K AS A FUNCTION OF APPLIED FIELD FOR $HoNi_2$, $ErNi_2$ AND $TmNi_2$.

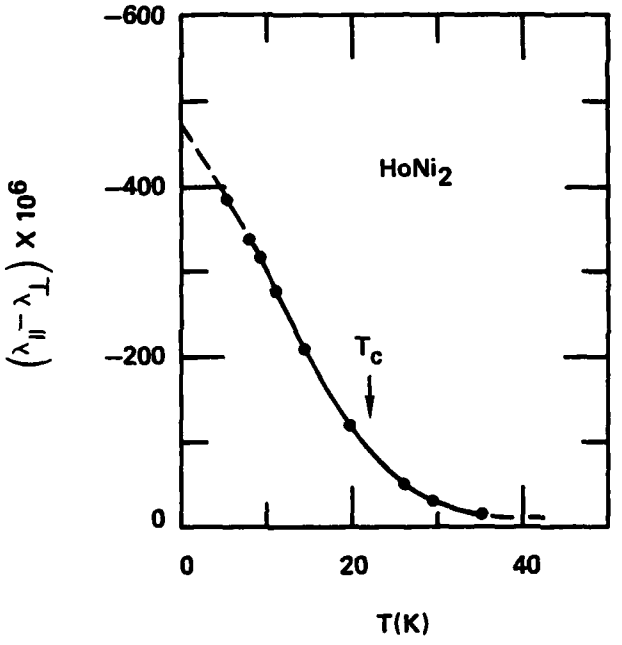


FIGURE 4 TEMPERATURE DEPENDENCE OF THE MAGNETOSTRICTION AT H=25kOe FOR $HoNi_2$. THE CURIE TEMPERATURE WAS TAKEN FROM BULK MAGNETIZATION MEASUREMENTS (REF. 8).

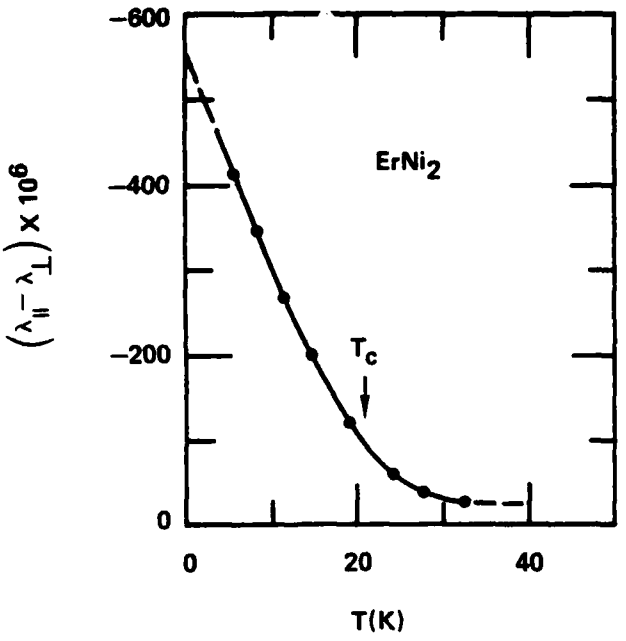


FIGURE 5 TEMPERATURE DEPENDENCE OF THE MAGNETOSTRICTION AT H=25kOe FOR $ErNi_2$. THE CURIE TEMPERATURE WAS TAKEN FROM BULK MAGNETIZATION MEASUREMENTS (REF. 8).

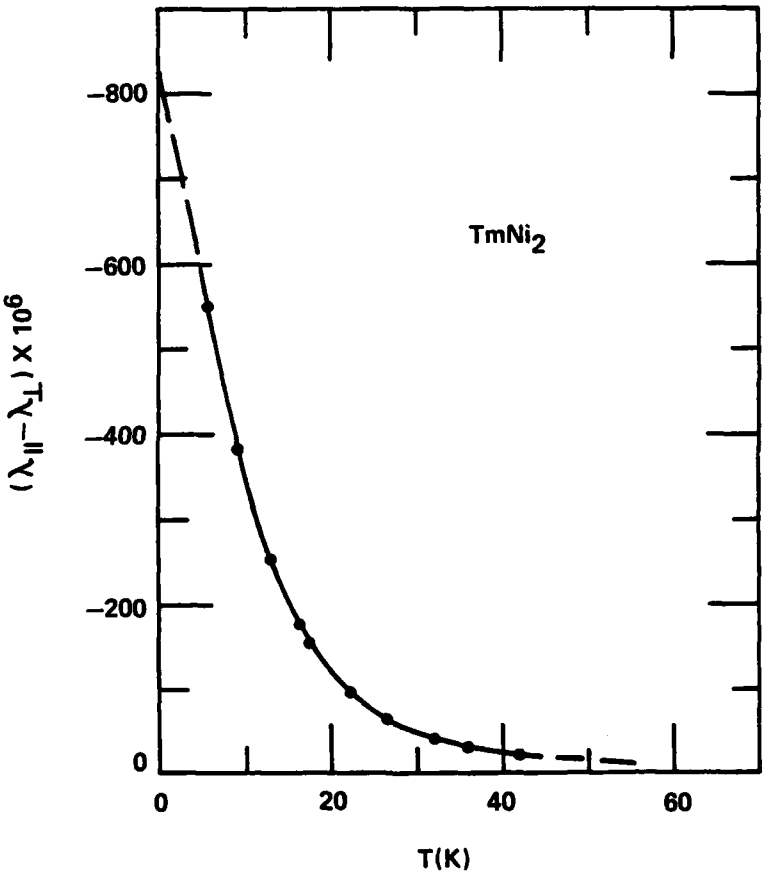


FIGURE 6 TEMPERATURE DEPENDENCE OF THE MAGNETOSTRICTION AT H=25kOe FOR $TmNi_2$.

DISTRIBUTION

| | Copies |
|---|---|
| Naval Air Development Center<br>Code 302 Attn: Mr. F. S. Williams<br>Warminster, PA 18964 | 1 |
| Naval Air Propulsion Test Center<br>Attn: Library<br>Trenton, NJ 08628 | 1 |
| Naval Air Systems Command<br>Attn: Code 52031<br>Code 52032<br>Washington, DC 20360 | 1<br>1 |
| Naval Construction Batallion<br>Attn: Materials Division<br>Civil Engineering Laboratory<br>Port Hueneme, CA 93043 | 1 |
| Naval Electronics Laboratory Center<br>Attn: Electron Materials<br>Sciences Division<br>San Diego, CA 92152 | 1 |
| Naval Facilities Engineering<br>Command<br>Attn: Code 03<br>Alexandria, VA 22331 | 1 |
| Naval Missile Center<br>Materials Consultant<br>Code 3312-1<br>Point Mugu, CA 92041 | 1 |
| Office of Naval Research<br>Branch Office<br>1030 East Green Street<br>Pasadena, CA 91106 | 1 |
| Office of Naval Research<br>San Francisco Area Office<br>One Hallidie Plaza Suite 601<br>San Francisco, CA 94102 | 1 |
| Commanding Officer<br>Office of Naval Research<br>Branch Office<br>536 South Clark Street<br>Chicago, IL 60605 | 1 |
| Commanding Officer<br>Office of Naval Research<br>Branch Office<br>Building 114, Section D<br>666 Summer Street<br>Boston, MA 02210 | 1 |
| Office of Naval Research<br>Department of the Navy<br>800 N. Quincy Street<br>Attn: Code 471<br>Code 102<br>Code 470<br>Arlington, VA 22217 | 1<br>1<br>1 |
| Naval Postgraduate School<br>Attn: Mechanical Engineering<br>Department<br>Monterey, CA 93940 | 1 |
| Dr. B. B. Rath<br>Naval Research Laboratory<br>Washington, DC 20375 | 1 |
| Naval Sea Systems Command<br>Attn: SEA-03B<br>Washington, D. C. 20362 | 1 |

| | Copies |
|---|---|
| Naval Research Laboratory | |
| Attn: Code 6000 | 1 |
| Code 6100 | 1 |
| Code 6300 | 1 |
| Code 6400 | 1 |
| Code 2627 | 1 |
| Washington, DC 20375 | |
| Naval Sea System Command | |
| Attn: Code 035 | 1 |
| Washington, DC 20362 | |
| Naval Ship Engineering Center | |
| Department of the Navy | |
| Attn: Code 6101 | 1 |
| Washington, DC 20360 | |
| David W. Taylor Naval Ship Research & Development Center | |
| Materials Department | |
| Annapolis, MD 21402 | 1 |
| Naval Undersea Center | |
| Attn: Library | 1 |
| San Diego, CA 92132 | |
| Naval Underwater System Center | |
| Attn: Library | 1 |
| Newport, RI 02840 | |
| Naval Weapons Center | |
| Attn: Library | 1 |
| China Lake, CA 93555 | |
| Scientific Advisor | |
| Commandant of the Marine Corps | |
| Attn: Code AX | 1 |
| Washington, DC 20380 | |
| Army Materials and Mechanics Research Center | |
| Attn: Research Programs Office | 1 |
| Watertown, MA 02172 | |
| Army Research Office | |
| Attn: Metallurgy & Ceramics Program | 1 |
| P.O. Box 12211 | |
| Triangle Park, NC 27709 | |
| Air Force Materials Laboratory | |
| Wright-Patterson AFB | |
| Dayton, OH 45433 | 1 |

| | Copies |
|---|---|
| Air Force Office of Scientific Research | |
| Attn: Chemical Science Directorate | 1 |
| Electronics & Solid State Sciences Directorate | 1 |
| Bldg. 410 | |
| Bolling Air Force Base | |
| Washington, DC 20332 | |
| NASA | |
| Lewis Research Center | |
| Attn: Library | 1 |
| 21000 Brookpark Road | |
| Cleveland, OH 44135 | |
| NASA Headquarters | |
| Attn: Code RRM | 1 |
| Washington, DC 20546 | |
| Defense Technical Information Center | |
| Cameron Station | |
| Alexandria, VA 22314 | 12 |
| National Bureau of Standards | |
| Attn: Metallurgy Division | 1 |
| Inorganic Materials Div. | 1 |
| Washington, DC 20234 | |
| Argonne National Laboratory | |
| Metallurgy Division | |
| P.O. Box 229 | |
| Lemont, IL 60439 | 1 |
| Defense Metals and Ceramics Information Center | |
| Battelle Memorial Institute | |
| 505 King Avenue | |
| Columbus, OH 43201 | 1 |
| Dr. R. B. Diegle | |
| Battelle Memorial Institute | |
| 505 King Avenue | |
| Columbus, Ohio 43201 | 1 |
| Brookhaven National Laboratory | |
| Attn: Research Library | 1 |
| Technical Information Division | |
| Upton, Long Island, NY 11973 | |

| | Copies |
|---|---|
| Professor P. R. Strutt<br>University of Connecticut<br>School of Engineering<br>Department of Metallurgy<br>Storrs, Connecticut 06268 | 1 |
| Dr. D. G. Ast<br>Cornell University<br>Ithaca, New York 14853 | 1 |
| Dr. F. E. Luborsky<br>General Electric Company<br>P.O. Box 8<br>Corporate R&D<br>Schenectady, NY 12301 | 1 |
| Dr. D. Turnbull<br>Harvard University<br>Department of Engineering & Applied Physics<br>Cambridge, Massachusetts 02139 | 1 |
| Library<br>Building 50, Rm 134<br>Lawrence Radiation Laboratory<br>Berkeley, CA 94550 | 1 |
| Los Alamos Scientific Laboratory<br>Attn: Report Librarian<br>P.O. Box 1663<br>Los Alamos, NM 87544 | 1 |
| Professor M. Cohen<br>Massachusetts Institute of Technology<br>Department of Metallurgy<br>Cambridge, Massachusetts 02139 | 1 |
| Dr. B. C. Giessen<br>Northeastern University<br>360 Huntington Avenue<br>Boston, Massachusetts 02139 | 1 |
| Metals and Ceramics Division<br>Oak Ridge National Laboratory<br>P.O. Box X<br>Oak Ridge, TN 37380 | 1 |
| Dr. J. Mahoney<br>Phrasor Technology<br>1536 Highland Avenue<br>Duate, California 91010 | 1 |

| | Copies |
|---|---|
| Professor William R. Walter<br>Polytechnic Institute of New York<br>Microwave Research Institute<br>Route 110<br>Farmingdale, NY 11735 | 1 |
| Professor G. S. Ansell<br>Rensselaer Polytechnic Institute<br>Dept. of Metallurgical Engineering<br>Troy, New York 02181 | 1 |
| Dr. N. S. Stoloff<br>Rensselaer Polytechnic Institute<br>Troy, New York 12181 | 1 |
| Dr. E. M. Breinan<br>United Technology Corporation<br>United Technology Research Labs.<br>East Hartford, Connecticut 06108 | 1 |
| Professor H. G. F. Wilsdorf<br>University of Virginia<br>School of Engineering & Applied Sciences<br>Charlottesville, Virginia 22903 | 1 |
| Director Applied Physics Laboratory<br>University of Washington<br>1013 Northeast Forthieth Street<br>Seattle, WA 98105 | 1 |

NDW-NSWC(W)-5605/1 (Rev. 5-78)

TO AID IN UPDATING THE DISTRIBUTION LIST FOR NAVAL SURFACE WEAPONS CENTER, WHITE OAK TECHNICAL REPORTS PLEASE COMPLETE THE FORM BELOW:

TO ALL HOLDERS OF NSWC/TR 80-303
by R. Abbundi, Code R45

DO NOT RETURN THIS FORM IF ALL INFORMATION IS CURRENT

A. FACILITY NAME AND ADDRESS *(OLD) (Show Zip Code)*

NEW ADDRESS *(Show Zip Code)*

B. ATTENTION LINE ADDRESSES:

C.

☐ REMOVE THIS FACILITY FROM THE DISTRIBUTION LIST FOR TECHNICAL REPORTS ON THIS SUBJECT.

D.
NUMBER OF COPIES DESIRED _____

GPO 930-784